


# PAMG-XR1 5056 Aluminum Honeycomb

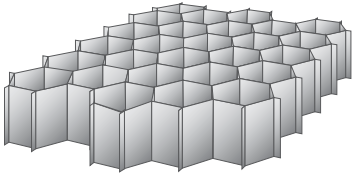

## Description:

---

PAMG-XR1 5056 aerospace grade aluminum honeycomb is a lightweight core material which offers superior strength over 5052 and 3003 aluminum honeycomb. PAMG-XR1 5056 honeycomb is made from 5056 aluminum alloy foil and meets all the requirements of AMS C7438.

## Applications:

---

PAMG-XR1 5056 honeycomb uses include aircraft floors, aircraft leading and trailing edges, missile wings, fan casings, fuel cells, fuselage components, helicopter rotor blades and navy bulkhead joiner panels. PAMG-XR1 5056 honeycomb is suitable for applications where materials conforming to AMS C7438 are required.

## Features:

---

- Elevated use temperatures
- High thermal conductivity
- Flame resistant
- Excellent moisture and corrosion resistance
- Fungi resistant
- Low weight / High strength
- Long shelf life. The mechanical properties referenced are maintained for 15 years minimum if not exposed to moisture, weather or any normal hazard.

## Availability:

---

PAMG-XR1 5056 honeycomb is available in four forms: unexpanded blocks, unexpanded slices, untrimmed expanded sheets and cut to size expanded sheets. It is also available with or without cell perforations to facilitate cell venting for certain applications.

<b>Cell Sizes:</b>	1/8" - 3/8"
<b>Densities:</b>	1.0 pcf - 12.0 pcf
<b>Sheet "Ribbon" (L):</b>	48" typical - 72" max
<b>Sheet "Transverse" (W):</b>	96" typical - 200" max
<b>Sheet Thickness (T):</b>	20"/34" max
<b>Tolerances:</b>	Length: + 6", - 0"
	Width: + 6", - 0"
	Thickness: ± .005" (under 4" thick) ± .062" (over 4" thick)
	Density: ± 10%
	Cell Size: ± 10%

**NOTE:** Special dimensions, sizes, tolerances, CNC machining and die cut to size can be provided upon request.


## Corrosion Resistance:

---

The chromated XR1 coating offers excellent protection for honeycomb cores exposed to corrosive environments, meeting the requirements of AMS C7438, CL2.

# PAMG-XR1 5056 honeycomb is specified as follows:

Trade Name - Corrosion Coating - Density - Cell Size - Foil Gauge - Perforation - Alloy

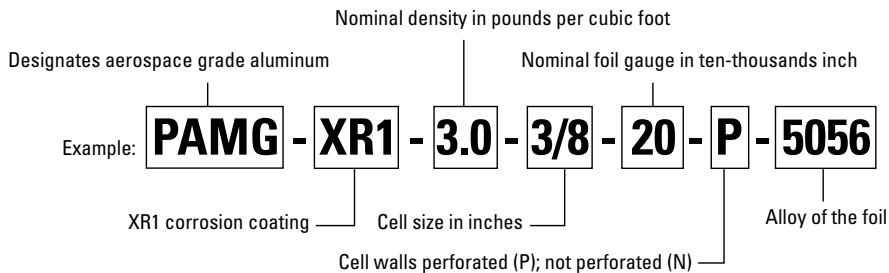

## PAMG-XR1 5056 Mechanical Properties

CELL SIZE		NOMINAL DENSITY		COMPRESSIVE STRENGTH (Bare)				PLATE SHEAR STRENGTH "L" DIRECTION		PLATE SHEAR MODULUS "L" DIRECTION		PLATE SHEAR STRENGTH "W" DIRECTION		PLATE SHEAR MODULUS "W" DIRECTION					
				Typical		Minimum		Typical		Minimum		Typical		Typical		Minimum		Typical	
in	mm	lb/Ft <sup>3</sup>	Kg/m <sup>3</sup>	psi	Mpa	psi	Mpa	psi	Mpa	psi	Mpa	ksi	Gpa	psi	Mpa	psi	Mpa	ksi	Gpa
1/8	3.2	3.1	50	350	2.41	260	1.79	283	1.95	200	1.38	50	0.34	147	1.01	110	0.76	23	0.16
1/8	3.2	4.5	72	690	4.76	500	3.45	431	2.97	350	2.41	80	0.55	251	1.73	205	1.41	34	0.23
1/8	3.2	6.1	98	1150	7.93	825	5.69	737	5.08	525	3.62	120	0.83	403	2.78	305	2.10	50	0.34
1/8	3.2	8.1	130	1753	12.09	1300	8.96	880	6.07	740	5.10	160	1.10	530	3.65	440	3.03	60	0.41
3/16	4.8	2.0	32	198	1.37	120	0.83	154	1.06	105	0.72	34	0.23	95	0.65	50	0.34	17	0.12
3/16	4.8	3.1	50	400	2.76	260	1.79	277	1.91	200	1.38	50	0.34	157	1.08	110	0.76	26	0.18
3/16	4.8	4.4	70	675	4.65	490	3.38	401	2.76	340	2.34	85	0.59	237	1.63	198	1.37	37	0.26
3/16	4.8	5.7	91	1000	6.90	735	5.07	532	3.67	480	3.31	108	0.74	330	2.28	280	1.93	48	0.33
5/32	4.0	2.6	42	267	1.84	185	1.28	194	1.34	152	1.05	41	0.28	130	0.90	80	0.55	16	0.11
5/32	4.0	3.8	61	511	3.52	375	2.59	342	2.36	272	1.88	60	0.41	195	1.34	155	1.07	30	0.21
1/4	6.4	1.6	26	122	0.84	80	0.55	105	0.72	78	0.54	21	0.14	70	0.48	38	0.26	9.5	0.07
1/4	6.4	2.3	37	248	1.71	155	1.07	170	1.17	130	0.90	37	0.26	108	0.74	62	0.43	18	0.12
1/4	6.4	3.4	54	426	2.94	315	2.17	296	2.04	230	1.59	52	0.36	161	1.11	130	0.90	22	0.15
1/4	6.4	4.3	69	650	4.48	465	3.21	374	2.58	325	2.24	78	0.54	220	1.52	190	1.31	29	0.20
1/4	6.4	5.2	83	840	5.79	645	4.45	423	2.92	425	2.93	84	0.58	306	2.11	245	1.69	32	0.22
3/8	9.6	1.0	16	55	0.38	35	0.24	55	0.38	45	0.31	13	0.09	35	0.24	25	0.17	6.1	0.04
3/8	9.6	1.6	26	118	0.81	80	0.55	113	0.78	78	0.54	21	0.14	64	0.44	38	0.26	9.5	0.07
3/8	9.6	2.3	37	230	1.59	155	1.07	170	1.17	130	0.90	32	0.22	95	0.65	62	0.43	15	0.10
3/8	9.6	3.0	48	380	2.62	250	1.72	245	1.69	190	1.31	60	0.41	145	1.00	100	0.69	19	0.13

Tested at 0.625" T per AMS STD 401 at room temperature.

The above data is based on various sample sizes and is for reference only.

Additional densities and configurations available upon request.



Plascore, Inc., employs a quality management system that is Nadcap, AS9100, ISO 9001 and ISO 14001 certified.

**IMPORTANT NOTICE:** The information contained in these materials regarding Plascore's products, processes, or equipment, is intended to be up to date, accurate, and complete. However, Plascore cannot warrant that this is always the case. Accordingly, it is a purchaser's or user's responsibility to perform sufficient testing and evaluation to determine the suitability of Plascore's products for a particular purpose. Information in these materials and product specifications does not constitute an offer to sell. Your submission of an order to Plascore constitutes an offer to purchase which, if accepted by Plascore, shall be subject to Plascore's terms and conditions of sale. **PLASCORE MAKES NO WARRANTIES OF ANY KIND REGARDING THESE MATERIALS OR INFORMATION, EITHER EXPRESS OR IMPLIED, INCLUDING WITHOUT LIMITATION THE IMPLIED WARRANTIES OF MERCHANTABILITY AND FITNESS FOR A PARTICULAR PURPOSE.** Plascore owns and shall retain all worldwide rights in its intellectual property, and any other trademarks used in these materials are the property of their respective owners. The information in these materials shall not be construed as an inducement, permission, or recommendation to infringe any patent or other intellectual property rights of any third parties.



### Corporate Headquarters

**Plascore Incorporated**  
 615 N. Fairview St.  
 Zeeland, MI 49464-0170  
 Phone (616) 772-1220  
 Toll Free (800) 630-9257  
 Fax (616) 772-1289  
 Email sales@plascore.com  
 Web www.plascore.com

### Europe

**Plascore GmbH&CoKG**  
 Feldborn 6  
 D-55444 Waldlaubersheim  
 Germany  
 Phone +49(0) 6707-9143 0  
 Fax +49(0) 6707-9143 40  
 Email sales.europe@plascore.com  
 Web www.plascore.de