



PAHD-XR1 5052 Aluminum Honeycomb

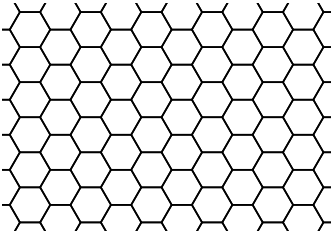


Description:

PAHD-XR1 5052 corrugated aerospace grade aluminum honeycomb is a high density core material which offers superior strength over expanded aluminum honeycomb. PAHD-XR1 5052 honeycomb is made from 5052 aluminum alloy foil and can be tested in accordance with customer requirements.

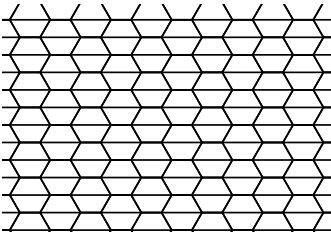

Applications:

PAHD-XR1 5052 honeycomb uses include engine nacelles, roll formed applications, energy absorption, anchor points, reinforcements, and other applications where light weight high strength materials are required. PAHD-XR1 5052 honeycomb is suitable for applications where materials with high compression and shear values are required.

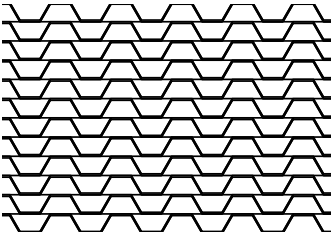

Cell Configurations:

- STD - Standard Hexagonal
- R2 - Bisected Hexagonal
- R2S[DG] - Bisected Staggered [Different Gauge]
- 2R2S - Reinforced Bisected Staggered
- R2S-Cross - Alternating Cell Axis for multi-axis strength (limited block size)

Availability:

PAHD-XR1 5052 honeycomb is available in three forms: untrimmed sheets, cut to size sheets, and machined components. Density is dependant on cell size and configuration.

Cell Sizes:	1/8" - 3/16"
Densities:	14.5 pcf - 55.0 pcf
Sheet "Ribbon" (L):	36" typical - 96" max
Sheet "Transverse" (W):	30" typical
Tolerances:	Length: +6", - 0" Width: +6", - 0" Thickness: ± .010" (under 4" thick)

Features:

- Elevated use temperatures
- High thermal conductivity
- Flame resistant
- Excellent moisture and corrosion resistance
- Fungi resistant
- High strength
- Machinable
- Roll formable


NOTE: Special dimensions, sizes, tolerances, and CNC machining can be provided upon request.

Corrosion Resistance:

The chromated XR1 coating offers excellent protection for honeycomb cores exposed to corrosive environments, meeting the requirements of AMS C7438 Rev A, CL2.

PAHD-XR1 5052 aluminum honeycomb is specified as follows:

Trade Name - Corrosion Coating - Density - Cell Size - Alloy - Cell Configuration

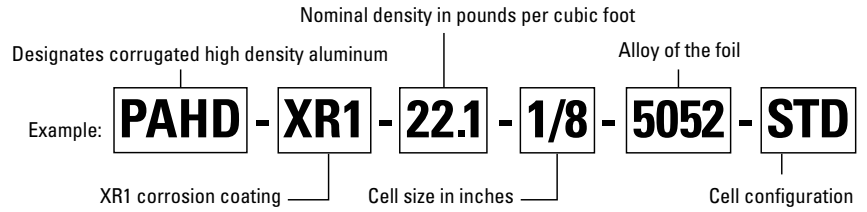

			PAHD-XR1 5052 Typical Mechanical Properties*				
			Compressive Strength (PSI)		Shear Strength (PSI)		Crush Strength (PSI)
CELL SIZE inch	NOMINAL DENSITY PCF	CONFIGURATION	BARE	STABILIZED	"L"	"W"	
1/8	14.5	STD	2900	3000	1700	800	2000
3/16	15.7	STD	3200	3300	1700	800	2000
1/8	22.1	STD	5200	5200	2500	1500	4050
3/16	22	R2SDG	5200	5200	2500	1500	2600
3/16	25	R2S	5500	5600	3000	1500	2800
1/8	30	R2S-Cross	-	-	-	-	2900
1/8	35	R2	7500	7700	4000	2000	6200
1/8	55	2R2S	8500	10000	4500	2250	8000

NOTE: Custom densities and configurations available upon request

Tested at 0.625" per the methods defined in AMS C7438 Rev A at room temperature.

*Minimum values may be up to 25% lower than typical values.



Plascore, Inc., employs a quality management system that is Nadcap, AS9100, ISO 9001 and ISO 14001 certified.

IMPORTANT NOTICE: The information contained in these materials regarding Plascore's products, processes, or equipment, is intended to be up to date, accurate, and complete. However, Plascore cannot warrant that this is always the case. Accordingly, it is a purchaser's or user's responsibility to perform sufficient testing and evaluation to determine the suitability of Plascore's products for a particular purpose. Information in these materials and product specifications does not constitute an offer to sell. Your submission of an order to Plascore constitutes an offer to purchase which, if accepted by Plascore, shall be subject to Plascore's terms and conditions of sale. **PLASCORE MAKES NO WARRANTIES OF ANY KIND REGARDING THESE MATERIALS OR INFORMATION, EITHER EXPRESS OR IMPLIED, INCLUDING WITHOUT LIMITATION THE IMPLIED WARRANTIES OF MERCHANTABILITY AND FITNESS FOR A PARTICULAR PURPOSE.** Plascore owns and shall retain all worldwide rights in its intellectual property, and any other trademarks used in these materials are the property of their respective owners. The information in these materials shall not be construed as an inducement, permission, or recommendation to infringe any patent or other intellectual property rights of any third parties.



Corporate Headquarters

Plascore Incorporated
 615 N. Fairview St.
 Zeeland, MI 49464-0170
 Phone (616) 772-1220
 Toll Free (800) 630-9257
 Fax (616) 772-1289
 Email sales@plascore.com
 Web www.plascore.com

Europe

Plascore GmbH&CoKG
 Feldborn 6
 D-55444 Waldlaubersheim
 Germany
 Phone +49(0) 6707-9143 0
 Fax +49(0) 6707-9143 40
 Email sales.europe@plascore.com
 Web www.plascore.de