


PN2 Aerospace Grade Meta-Aramid Fiber Honeycomb

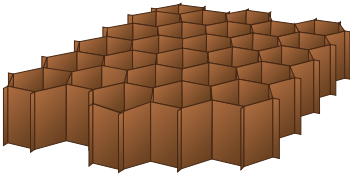

Description:

PN2 aerospace grade aramid fiber honeycomb exhibits outstanding flammability properties. It is manufactured from Meta-Aramid paper and coated with a heat resistant phenolic resin.

Applications:

PN2 honeycomb uses include aircraft galleys, flooring, partitions, aircraft leading and trailing edges, missile wings, radomes, antennas, military shelters, fuel tanks, helicopter rotor blades and navy bulkhead joiner panels.

Features:

- Fire resistant (self extinguishing)
- High strength to weight ratio
- Corrosion resistant
- Excellent dielectric properties
- Thermally insulating
- High toughness
- Excellent creep and fatigue performance
- Good thermal stability
- Densities as low as 1.5 lb/ft³ (24 kg/m³)
- Over expanded cell configuration suitable for forming simple curves
- Compatible with most adhesives used in sandwich composites
- Long shelf life. The mechanical properties referenced are maintained for 10 years minimum if not exposed to moisture, weather or any normal hazard.

Availability:

PN2 honeycomb is available in sheets, blocks or cut to size pieces in both regular hexagonal and over expanded (OV) cell configurations.

Cell Sizes:	1/8" - 3/8"
Densities:	1.8 pcf - 9.0 pcf
Sheet "Ribbon" (L):	48" typical
Sheet "Transverse" (W):	96" typical
Tolerances:	Length: + 3", - 0" (60" for OV) Width: + 6", - 0" Thickness: ± .006" (under 2" thick) Density: ± 10% Cell Size: ± 10%


NOTE: Special dimensions, sizes, tolerances and specifications can be provided upon request.

PN2 aerospace grade Meta-Aramid fiber honeycomb is specified as follows:

Material - Cell Size - Density - Cell Configuration

Designates aerospace grade Meta-Aramid fiber

The nominal density in pounds per cubic foot

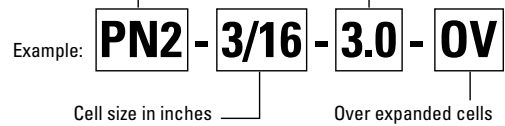

PN2 Meta-Aramid Mechanical Properties																			
CELL SIZE		NOMINAL DENSITY		COMPRESSIVE STRENGTH (BARE)				PLATE SHEAR STRENGTH "L" DIRECTION				PLATE SHEAR MODULUS "L" DIRECTION		PLATE SHEAR STRENGTH "W" DIRECTION				PLATE SHEAR MODULUS "W" DIRECTION	
				Typical		Minimum		Typical		Minimum		Typical		Typical		Minimum		Typical	
in	mm	lb/Ft ³	Kg/m ³	psi	Mpa	psi	Mpa	psi	Mpa	psi	Mpa	ksi	Gpa	psi	Mpa	psi	Mpa	ksi	Gpa
1/8	3.2	1.8	29	102	0.70	70	0.48	87	0.60	65	0.45	4.0	0.03	49	0.34	36	0.25	1.7	0.01
1/8	3.2	2.0	32	143	0.99	114	0.79	107	0.74	69	0.48	4.9	0.03	58	0.40	40	0.28	2.2	0.02
1/8	3.2	2.3	37	199	1.37	137	0.94	126	0.87	73	0.50	5.3	0.04	68	0.47	48	0.33	2.5	0.02
1/8	3.2	3.0	48	303	2.09	180	1.24	196	1.35	162	1.12	6.7	0.05	100	0.69	85	0.59	3.8	0.03
1/8	3.2	4.0	64	544	3.75	330	2.28	266	1.83	225	1.55	9.0	0.06	143	0.99	100	0.69	5	0.03
1/8	3.2	4.5	72	680	4.69	450	3.10	291	2.01	200	1.38	10.5	0.07	154	1.06	117	0.81	6	0.04
1/8	3.2	5.0	80	810	5.58	600	4.14	319	2.20	235	1.62	11.7	0.08	175	1.21	120	0.83	6.5	0.04
1/8	3.2	6.0	96	1113	7.67	800	5.52	390	2.69	260	1.79	13.5	0.09	248	1.71	135	0.93	7	0.05
1/8	3.2	8.0	128	1766	12.18	1100	7.58	422	2.91	355	2.45	16.7	0.12	295	2.03	190	1.31	11	0.08
1/8	3.2	9.0	144	2250	15.51	1400	9.65	445	3.07	370	2.55	18.0	0.12	311	2.14	240	1.65	13	0.09
3/16	4.8	1.4	22	52	0.36	40	0.28	45	0.31	23	0.16	2.6	0.02	31	0.21	20	0.14	1.7	0.01
3/16	4.8	1.8	29	91	0.63	60	0.41	85	0.59	35	0.24	4.1	0.03	51	0.35	30	0.21	2.2	0.02
3/16	4.8	2.0	32	130	0.90	90	0.62	106	0.73	72	0.50	4.4	0.03	63	0.43	40	0.28	2.5	0.02
3/16	4.8	3.0	48	330	2.28	180	1.24	176	1.21	125	0.86	6.0	0.04	118	0.81	67	0.46	4.5	0.03
3/16	4.8	4.0	64	565	3.90	320	2.21	240	1.65	225	1.55	8.2	0.06	162	1.12	112	0.77	5.7	0.04
3/16	4.8	6.0	96	1061	7.32	580	4.00	396	2.73	330	2.28	14.2	0.10	250	1.72	150	1.03	7.9	0.05
1/4	6.4	1.5	24	80	0.55	45	0.31	64	0.44	45	0.31	3.3	0.02	37	0.26	23	0.16	1.8	0.01
1/4	6.4	2.0	32	149	1.03	80	0.55	104	0.72	72	0.50	4.0	0.03	66	0.46	36	0.25	2.9	0.02
1/4	6.4	3.1	50	255	1.76	180	1.24	178	1.23	135	0.93	6.3	0.04	112	0.77	60	0.41	3.5	0.02
1/4	6.4	4.0	64	472	3.25	310	2.14	244	1.68	200	1.38	8.0	0.06	150	1.03	96	0.66	4.5	0.03
3/8	9.6	1.5	24	95	0.66	45	0.31	70	0.48	45	0.31	3.0	0.02	35	0.24	23	0.16	1.5	0.01
3/8	9.6	2.0	32	140	0.97	80	0.55	90	0.62	72	0.50	3.7	0.03	55	0.38	36	0.25	2.3	0.02
3/8	9.6	3.0	48	309	2.13	175	1.21	204	1.41	110	0.76	6.8	0.05	117	0.81	55	0.38	4	0.03
1/8 OV	3.2	3.0	48	300	2.07	200	1.38	133	0.92	120	0.83	4.1	0.03	137	0.94	120	0.83	6	0.04
3/16 OV	4.8	1.8	29	92	0.63	70	0.48	56	0.39	45	0.31	2.0	0.01	64	0.44	35	0.24	3.6	0.02
3/16 OV	4.8	2.0	32	119	0.82	90	0.62	69	0.48	50	0.34	2.1	0.01	82	0.57	40	0.28	4.3	0.03
3/16 OV	4.8	2.3	37	162	1.12	112	0.77	79	0.54	55	0.38	2.3	0.02	96	0.66	44	0.30	5.2	0.04
3/16 OV	4.8	3.0	48	316	2.18	250	1.72	115	0.79	95	0.65	3.0	0.02	140	0.97	95	0.65	6.8	0.05
3/16 OV	4.8	4.0	64	521	3.59	350	2.41	155	1.07	120	0.83	4.0	0.03	225	1.55	125	0.86	9.6	0.07
1/4 OV	6.4	3.0	48	320	2.21	210	1.45	103	0.71	90	0.62	3.2	0.02	131	0.90	90	0.62	7.4	0.05
3/8 OV	9.6	3.0	48	245	1.69	185	1.28	128	0.88	105	0.72	3.6	0.02	164	1.13	115	0.79	7	0.05

Tested at 0.500" T per AMS STD 401 at room temperature. The above data is based on various sample sizes and is for reference only.

Additional densities and configurations available upon request.



Plascore, Inc., employs a quality management system that is Nadcap, AS9100, ISO 9001 and ISO 14001 certified.

IMPORTANT NOTICE: The information contained in these materials regarding Plascore's products, processes, or equipment, is intended to be up to date, accurate, and complete. However, Plascore cannot warrant that this is always the case. Accordingly, it is a purchaser's or user's responsibility to perform sufficient testing and evaluation to determine the suitability of Plascore's products for a particular purpose. Information in these materials and product specifications does not constitute an offer to sell. Your submission of an order to Plascore constitutes an offer to purchase which, if accepted by Plascore, shall be subject to Plascore's terms and conditions of sale. PLASCORE MAKES NO WARRANTIES OF ANY KIND REGARDING THESE MATERIALS OR INFORMATION, EITHER EXPRESS OR IMPLIED, INCLUDING WITHOUT LIMITATION THE IMPLIED WARRANTIES OF MERCHANTABILITY AND FITNESS FOR A PARTICULAR PURPOSE. Plascore owns and shall retain all worldwide rights in its intellectual property, and any other trademarks used in these materials are the property of their respective owners. The information in these materials shall not be construed as an inducement, permission, or recommendation to infringe any patent or other intellectual property rights of any third parties.



Corporate Headquarters

Plascore Incorporated
 615 N. Fairview St.
 Zeeland, MI 49464-0170
 Phone (616) 772-1220
 Toll Free (800) 630-9257
 Fax (616) 772-1289
 Email sales@plascore.com
 Web www.plascore.com

Europe

Plascore GmbH&CoKG
 Feldborn 6
 D-55444 Waldlaubersheim
 Germany
 Phone +49(0) 6707-9143 0
 Fax +49(0) 6707-9143 40
 Email sales.europe@plascore.com
 Web www.plascore.de